

Metamagnetism and critical fluctuations in high quality single crystals of the bilayer ruthenate $\text{Sr}_3\text{Ru}_2\text{O}_7$

R. S. Perry, L. M. Galvin, S. A. Grigera, L. Capogna, A. J. Schofield, A. P. Mackenzie
School of Physics and Astronomy, University of Birmingham, Edgbaston, Birmingham B15 2TT, United Kingdom.

M. Chiao and S. R. Julian
Cavendish Laboratory, University of Cambridge, Madingley Road, Cambridge CB3 0HE, United Kingdom.

S. Ikeda^{1,2}, S. Nakatsuji² and Y. Maeno^{2,3}

¹*Electrotechnical Laboratory, Tsukuba, Ibaraki 305-8568, Japan.*

²*Department of Physics, Kyoto University, Kyoto 606-8502, Japan.*

³*CREST, Japan Science and Technology Corporation, Kawaguchi, Saitama 332-0012, Japan.*

C. Pfleiderer

University of Karlsruhe, Institute of Physics, Kaiserstr. 12, D-76128 Karlsruhe, Germany.

We report the results of low temperature transport, specific heat and magnetisation measurements on high quality single crystals of the bilayer perovskite $\text{Sr}_3\text{Ru}_2\text{O}_7$, which is a close relative of the unconventional superconductor Sr_2RuO_4 . Metamagnetism is observed, and transport and thermodynamic evidence for associated critical fluctuations is presented. These relatively unusual fluctuations might be pictured as variations in the Fermi surface topography itself. No equivalent behaviour has been observed in the metallic state of Sr_2RuO_4 .

PACS 71.27.+a, 75.30.Kz

Research over the past decade has shown the potential of perovskite ruthenate metals to play a pivotal role in our understanding of the behaviour of strongly correlated electrons. The position of the Fermi level in bands resulting from the hybridisation of oxygen 2p and ruthenium 4d levels leads to ground state behaviour covering a wider range than that seen in almost any other transition metal oxide series. Pseudocubic SrRuO_3 is a rare example of an itinerant ferromagnet based on 4d electrons, and has a good lattice match to the cuprates [1,2]. Sr_2RuO_4 has the layered perovskite structure with a single RuO_2 plane per formula unit. It is strongly two-dimensional, and shows a Pauli-like paramagnetic susceptibility [3]. It is best known for its unconventional superconductivity [3], which is thought to involve spin triplet pairing [4]. Structural distortions in Sr-based ruthenates are either small or absent, but substituting Ca for Sr introduces larger rotations of the Ru-O octahedra, causing bandwidth narrowing and changes to the crystal field splitting. Thus, although Ca and Sr are both divalent cations, the properties of the Ca-based materials are markedly different. CaRuO_3 is a paramagnetic metal with a large mass enhancement [5], while Ca_2RuO_4 is an antiferromagnetic insulator [6]. This diversity shows that the ruthenates are characterised by a series of competing, nearly degenerate instabilities, giving a clear motivation for the careful investigation of all the compounds in the series. An even more important feature of the ruthenates is that, in contrast to 3d oxides such as most manganites and many cuprates, no explicit chemical doping is required to produce metallic conduction. This gives a unique opportunity

to probe a wide range of correlated electron physics in the low disorder limit, leading to considerable advances in understanding. The superconductivity of Sr_2RuO_4 , for example, is strongly disorder-dependent [7], and further examples of unconventional superconductivity may be expected in other ruthenates if they can be grown with mean free paths as long as those of Sr_2RuO_4 . Of particular interest is the subject of this study, $\text{Sr}_3\text{Ru}_2\text{O}_7$, which has a Ru-O bilayer per formula unit, and hence an effective dimensionality which is intermediate between those of Sr_2RuO_4 and SrRuO_3 .

The synthesis of $\text{Sr}_3\text{Ru}_2\text{O}_7$ in polycrystalline form has been reported by several groups over the past three decades [8–10], but investigations of its electrical and magnetic properties were not carried out until the past few years. There has been some variation in the reports and interpretation of its ground state. Cava and co-workers showed that the magnetic susceptibility (χ) of powders obeyed a Curie-Weiss law with a maximum in the susceptibility at approximately 20K and a negative Weiss temperature, which they interpreted in a local moment picture as antiferromagnetism [11]. Early reports on single crystals grown from a SrCl_2 flux in Pt crucibles, however, gave evidence for weak itinerant ferromagnetism [12]. Elastic neutron scattering measurements on polycrystalline materials showed no sign of either kind of long-range order [13].

The lack of long-range order was confirmed by Ikeda and co-workers [14], who succeeded in growing much purer crystals (residual in-plane resistivity, ρ_{res} , of 3–4 $\mu\Omega\text{cm}$) in an image furnace. The magnetic suscep-

tibility of these crystals reproduces the basic features of the paramagnetic susceptibility reported in ref. 11, with a pronounced maximum at approximately 16K. Although the resistivity has an anisotropy ratio of several hundred, the susceptibility is much more isotropic, with an anisotropy at 16K of only 20%. At lower temperatures, below 5K, it becomes completely isotropic and temperature independent. The low temperature value of $\chi = 1.5 \times 10^{-2} \text{emu/mol-Ru}$ is over an order of magnitude larger than that of Sr_2RuO_4 , while values between 1.5 and 2.5 times larger have been reported for the electronic specific heat per Ru mole [14,15]. Combined with the observation of a T^2 dependence of the resistivity (ρ) in the same temperature range, the data strongly suggest that $\text{Sr}_3\text{Ru}_2\text{O}_7$ enters a Fermi liquid metallic state at low temperatures. Published electronic band structure calculations predict a Fermi surface which is very similar to that of Sr_2RuO_4 [16], giving no expectation of substantial differences between the properties of the two materials.

Here, we report the results of low temperature transport, magnetic and thermodynamic measurements on the crystals studied in ref. 14 and some even cleaner ones ($\rho_{\text{res}} = 2 \mu\Omega\text{cm}$). We conclude that the low temperature properties of $\text{Sr}_3\text{Ru}_2\text{O}_7$ are strongly influenced by critical fluctuations associated with metamagnetism, something that has never been observed in Sr_2RuO_4 .

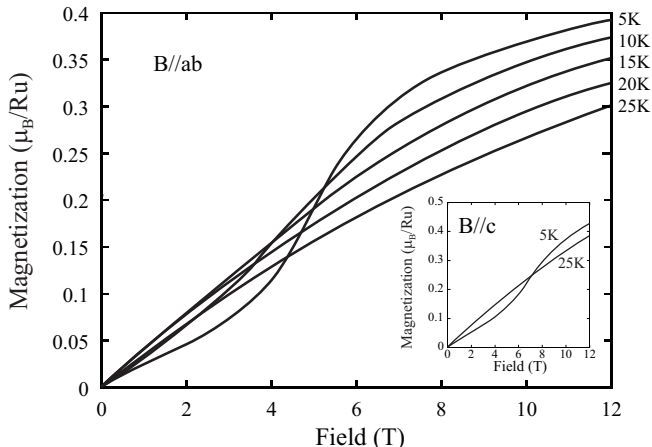


FIG. 1. The magnetisation of single crystal $\text{Sr}_3\text{Ru}_2\text{O}_7$ for magnetic fields applied in the ab plane. The high field data drop monotonically, with the highest value seen at 5K. Metamagnetism is clearly seen in the 5K and 10K data, at a field of approximately 5.5 tesla. No anisotropy is observed for different field directions within the ab plane (data not shown). Inset: Data at 5K and 25K with the magnetic field applied along the c axis. For this orientation the metamagnetic field is approximately 7.7 tesla (see Fig. 2).

Several growth runs of single crystals of $\text{Sr}_3\text{Ru}_2\text{O}_7$ were performed crucible-free in an image furnace in Kyoto. The resistivity of over fifty pieces taken from three growth rods was studied down to 4K using standard low

frequency ac methods in a small continuous flow cryostat. Residual resistivities ranging between $2 \mu\Omega\text{cm}$ and $15 \mu\Omega\text{cm}$ were observed, with most samples from the latter batches toward the high purity end of the range. Six of these were used for further study. Magnetisation measurements were performed down to 5K in a commercial vibrating sample magnetometer. Magneto-transport was studied at ambient pressure in both ^4He systems and a dilution refrigerator in Birmingham, and in a ^4He system in Karlsruhe. Specific heat measurements were performed in Kyoto using commercial magneto-thermal apparatus.

Our magnetisation results for $\text{Sr}_3\text{Ru}_2\text{O}_7$ are summarised in Fig. 1. For magnetic fields applied in the ab plane, a rapid super-linear rise in the magnetization is seen with a characteristic field of approximately 5.5 tesla at 5K. Such behaviour can be described as metamagnetism (for further discussion see below). As the temperature is raised, the metamagnetism disappears. The data give no evidence for it moving to higher field; the dominant effect is a broadening which makes it impossible to define. We have checked extensively for anisotropy with respect to the direction of the in-plane field, but none is observed within our resolution. There is some anisotropy if the field is applied along c , as shown in the inset. Although data were also taken at 10, 15 and 20K, they lie sufficiently close to confuse the plot, so have been omitted for clarity.

In order to obtain information on the metamagnetism to lower temperatures, we have studied its effects on the magnetoresistance (MR). Field sweeps to 14 tesla were performed between 50 mK and 20K for three standard configurations of the in-plane MR ρ : $B \parallel c$, $I \parallel ab$; $B \parallel I \parallel ab$ and $(B \perp I) \parallel ab$. The results are summarised in Fig. 2, in which a small subset of representative data is presented. For $B \parallel c, I \parallel ab$, the weak-field MR is quadratic in B . At higher fields, the metamagnetism is clearly seen in the MR. For $T \geq 5\text{K}$, the width of the feature is similar to that seen in the magnetisation, but at low temperatures it sharpens considerably, although there is evidence for extra structure at 11 tesla. For $B \parallel ab$ there is clear evidence of a split transition for both $B \parallel I$ and $B \perp I$. The transport measurements show that the metamagnetic transition field is essentially temperature independent for any direction of the applied field.

The term metamagnetism can be applied to qualitatively different physical phenomena. In insulators, it describes changes from ordered antiferromagnetic states at low field to ferromagnetically polarized states at high field via ‘spin-flip’ or ‘spin-flop’ processes [17]. In metallic systems such as $\text{Sr}_3\text{Ru}_2\text{O}_7$, the change in magnetization is due to a rapid change from a paramagnetic state at low fields to a more highly polarized state at high fields, via either a crossover or a phase transition. Although the distinction between a crossover and a phase transition can be an important one, in this case it is less relevant, because some of the basic physics is common

to both. Firstly, the observation of itinerant metamagnetism demonstrates the existence of strong ferromagnetic coupling in the system. Secondly, low temperature critical points are likely in either scenario. A crossover might be linked to close proximity in phase space to a quantum critical point that can be reached only by the application of some other control parameter. If the metamagnetism is due to a $T = 0$ phase transition along the magnetic field axis, the transition would be expected to be first order (since it is like a density transition of spins in the presence of a symmetry-breaking field). However, the first order transition line might terminate in a critical point at very low temperatures. A natural question, then, is whether there is evidence for critical fluctuations associated with the metamagnetism in $\text{Sr}_3\text{Ru}_2\text{O}_7$. To address this issue, we have performed measurements of the temperature-dependent resistivity and specific heat.

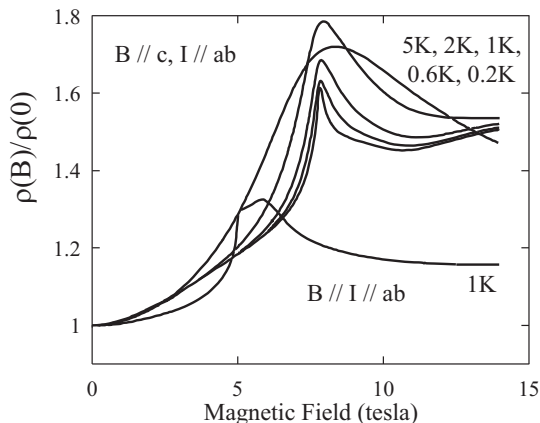


FIG. 2. The magnetoresistance (MR) of single crystal $\text{Sr}_3\text{Ru}_2\text{O}_7$ at a series of temperatures below 1K. For $B \parallel c$, the very broad peak at 5K (comparable to the total width of the feature seen in $M(B)$) sharpens considerably at low temperatures. For in-plane fields, the low temperature MR gives evidence for some peak splitting, as shown by data at 1K for this orientation.

In Fig. 3 we show a colour plot of the power-law behaviour of the resistivity of $\text{Sr}_3\text{Ru}_2\text{O}_7$ as a function of temperature and field, for $I \parallel ab \parallel B$. At low and high field, the quadratic temperature dependence expected of a Fermi liquid is seen at sufficiently low temperature, but near the metamagnetic field, the Fermi liquid region is suppressed to below our lowest temperature of measurement (2.5K for these precise temperature sweeps). These data are strongly suggestive of the existence of a critical point at a temperature low on the scale of the measurement temperature, at a field close to the metamagnetic field. They do not constrain it to lie exactly on the field axis, but the applied field is clearly pushing the system very close to it, and its associated critical fluctuations are playing a central role in determining the properties of the metallic state.

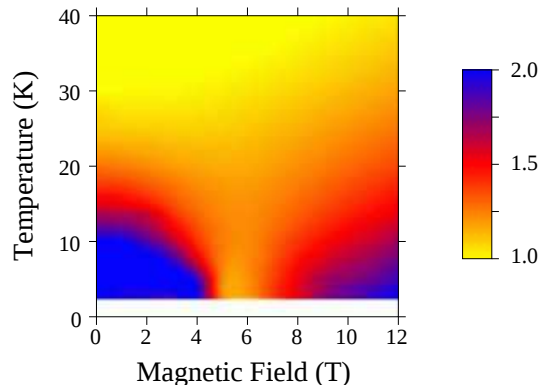


FIG. 3. The evolution of the temperature dependence of the resistivity of $\text{Sr}_3\text{Ru}_2\text{O}_7$ as a function of temperature with $B \parallel I \parallel ab$. The plot was constructed by interpolating the results of temperature sweeps at fourteen values of applied field (0 to 12 tesla in 1 tesla steps, with an additional sweep at 5.5 tesla). The colours show the change in the parameter α for a temperature-dependent resistivity of the form T^α . The T^2 behaviour expected of a Fermi liquid is observed at low temperatures only for fields well away from the metamagnetic field of approximately 5.5 tesla identified from Fig. 2.

Measurement of the specific heat gives further experimental support for the existence of critical fluctuations. Data for the electronic specific heat (C_{el}) divided by temperature are shown in Fig. 4. In zero field, C_{el}/T (a measure of the quasiparticle mass) rises as the temperature falls below 20K, but then crosses over at lower temperatures on a scale similar (but not identical) to the crossover to the quadratic dependence of the resistivity seen in Fig. 3. The application of fields parallel to the c axis suppresses this crossover, so that C_{el}/T rises steeply at low temperatures. At 9 tesla there is evidence for the divergence being cut off at low temperatures, but at 7.7 tesla, no cut-off is seen. As well as giving thermodynamic support for the critical fluctuations suggested by the transport measurements, the specific heat data emphasise the closeness of the link between the metamagnetism and these fluctuations. If the critical point dominating the fluctuations seen in Fig. 3 were primarily controlled by some parameter other than the field, then changing the field orientation would be expected to make very little difference. Here, however, we have tuned into the divergence of C_{el}/T by cooling at the metamagnetic field for $B \parallel c$ (identified as 7.7 tesla by the peak in Fig. 2) rather than the value of approximately 5.5 tesla that would be deduced from Figs. 2 and 3 for $B \parallel ab$.

We believe that the above data give good evidence for a close association between metamagnetism and critical fluctuations in $\text{Sr}_3\text{Ru}_2\text{O}_7$. The best way to view itinerant metamagnetism is that the extra moment is generated by a polarization of the up and down spin Fermi surfaces, so our results suggest that $\text{Sr}_3\text{Ru}_2\text{O}_7$ is an excellent material in which to study a very interesting form of low temperature fluctuation, that of the Fermi surface itself.

Although this is a $\mathbf{q} = 0$ picture, the polarized and unpolarized Fermi surfaces are likely to have different nesting properties in a nearly two-dimensional material, so a coupling with fluctuations at higher $\mathbf{q}$ is to be expected.

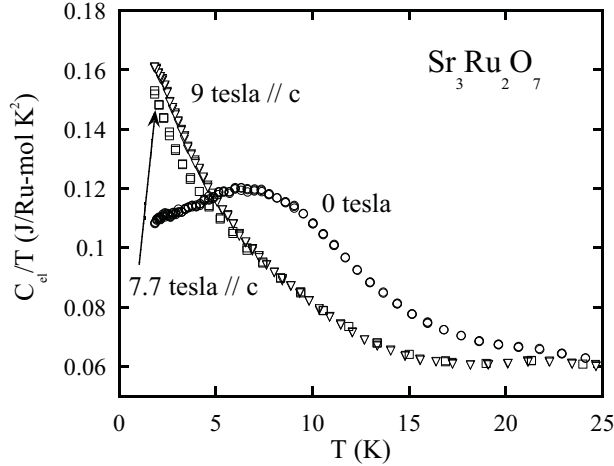


FIG. 4. The electronic specific heat divided by temperature for $\text{Sr}_3\text{Ru}_2\text{O}_7$ at low temperatures, for magnetic fields applied parallel to c . Subtracting the T^3 lattice contribution gave a Debye temperature of 360K, in good agreement with previous work on polycrystalline samples [15]. Apparently divergent behaviour is seen when the field is tuned to the metamagnetic peak for this field orientation, identified from Fig. 2 to be 7.7 tesla. If the field is increased to 9 tesla, the divergence is cut off.

Itinerant electron metamagnetism has previously been observed in several systems (notable recent examples are MnSi [18] and CeRu_2Si_2 [19]), but this is, to our knowledge, the first time that such clear evidence has been seen for a magnetic field driving a system closer to criticality. The fact that it has been seen in a close structural relative of Sr_2RuO_4 gives the result further significance, and provides a second motivation for more detailed investigation of the spin fluctuations in $\text{Sr}_3\text{Ru}_2\text{O}_7$. There is good and growing evidence for triplet superconductivity in Sr_2RuO_4 , but, so far, little experimental evidence for the strong low- $\mathbf{q}$ fluctuations that might naïvely be expected to give the underlying binding mechanism. The only structure that has been observed is a nesting feature at $(0.6 \pi/a, 0.6 \pi/a)$ [20], and no metamagnetism has been observed in fields of up to 33 tesla [21]. In $\text{Sr}_3\text{Ru}_2\text{O}_7$, our results in combination with those of ref. 14 clearly demonstrate the existence of a low $\mathbf{q}$ enhancement, but no superconductivity has been observed down to our best residual resistivity of $2 \mu\Omega\text{cm}$. It will be very interesting to see if there is a significant enhancement at high $\mathbf{q}$ as well, and to investigate the underlying reasons for the pronounced differences in the magnetic properties between the two materials. In this respect, the orthorhombicity recently reported in $\text{Sr}_3\text{Ru}_2\text{O}_7$ [22] may prove to be significant. More generally, continued work on $\text{Sr}_3\text{Ru}_2\text{O}_7$ is likely to play an important role

in efforts to understand unconventional superconductivity in the ruthenates. A search for quantum oscillations, an investigation of the effect of pressure on the metamagnetism and inelastic neutron scattering measurements are all desirable, in combination with further improvements in sample purity.

In conclusion, we have presented evidence that the low temperature properties of $\text{Sr}_3\text{Ru}_2\text{O}_7$ are strongly influenced by critical fluctuations associated with the presence of metamagnetism. Our observations highlight important and somewhat unexpected differences with the metallic state that exists in its well-studied structural relative, the unconventional superconductor Sr_2RuO_4 .

We are grateful to C. Bergemann, N. R. Cooper, V. J. Emery, E. M. Forgan, H. von Loehneysen, G. G. Lonzarich, A. J. Millis, A. Rosch, and D. J. Singh for fruitful discussions. This work was supported by the EPSRC (UK), the Royal Society, the Leverhulme Trust, NSERC (Canada), CREST-NST (Japan) and ESF (FERLIN Collaboration).

-
- [1] P. B. Allen *et al.*, Phys. Rev. B **53**, 4393 (1996).
 - [2] L. Klein *et al.*, J. Phys.: Cond. Matt. **8**, 10111 (1996).
 - [3] Y. Maeno *et al.*, Nature **372**, 532 (1994).
 - [4] K. Ishida *et al.*, Nature **396**, 658 (1998).
 - [5] G. Cao *et al.*, Phys. Rev. B **56**, 321 (1997).
 - [6] S. Nakatsuji, S. Ikeda and Y. Maeno, J. Phys. Soc. Jpn. **66**, 1868 (1997).
 - [7] A. P. Mackenzie *et al.*, Phys. Rev. Lett. **80**, 161 (1998).
 - [8] J. A. Kafalas and J. M. Longo, J. Solid State Chem. **4**, 55 (1972).
 - [9] Hk. Müller-Buschbaum and J. Wilkens, Z. Anorg. Allg. Chem. **591**, 161 (1990).
 - [10] T. Williams *et al.*, Mater. Res. Bull. **26**, 763 (1991).
 - [11] R. J. Cava *et al.*, J. Solid State Chem. **116**, 141 (1995).
 - [12] G. Cao, S. McCall and J. E. Crow, Phys. Rev. B **55**, R672 (1997).
 - [13] Q. Huang *et al.*, Phys. Rev. B **58**, 8515 (1998).
 - [14] S. Ikeda *et al.*, cond-mat/0002147, to be published in Phys. Rev. B.
 - [15] S. Ikeda, Y. Maeno and T. Fujita, Phys. Rev. B **57**, 978 (1998).
 - [16] I. Hase and Y. Nishihara, J. Phys. Soc. Jpn. **66**, 3517 (1997).
 - [17] For example E. Strykowski and N. Giordano, Adv. Phys. **26**, 487 (1977).
 - [18] For example C. Thessieu *et al.*, J. Phys.:Cond. Matt. **9**, 6677 (1997).
 - [19] J. M. Mignot *et al.*, J. Magn. Magn. Mat. **76&77**, 97 (1997).
 - [20] Y. Sidis *et al.*, Phys. Rev. Lett. **83**, 3320 (1999).
 - [21] E. Ohmichi *et al.*, Phys. Rev. B **61**, 7101 (2000).
 - [22] H. Shaked, J. D. Jorgensen, O. Chmaissem, S. Ikeda and Y. Maeno, unpublished.